



Company Address	IDT Industrie- und Dichtungstechnik GmbH Werk Kupferring, Gewerbering 6, 09456 Annaberg-Buchholz, Germany	According to DIN EN 13555 2014-07
Gasket Type	Elastik-Dichtung ED10 WS 7110/WS 7550	
Sealing element dimensions [mm]	49xs92x4.0	

L [mg/(s*m)]	Q _{min/L} [MPa]	Minimum stress to seal Q _{min/L} (at assembly), Q _{Smin/L} (after off-loading) for p = 10 bar										
		Q _{Smin/L} [MPa]										
		Q _A = 10 MPa	Q _A = 20 MPa	Q _A = 30 MPa	Q _A = 40 MPa	Q _A = 60 MPa	Q _A = 80 MPa					
10 ⁻⁰	5	5	5	5	5	5						
10 ⁻¹	5	5	5	5	5	5						
10 ⁻²	5	5	5	5	5	5						
10 ⁻³	5	5	5	5	5	5						
10 ⁻⁴	5	5	5	6	5	5						
10 ⁻⁵	39				35	50						
10 ⁻⁶												
10 ⁻⁷												
10 ⁻⁸												

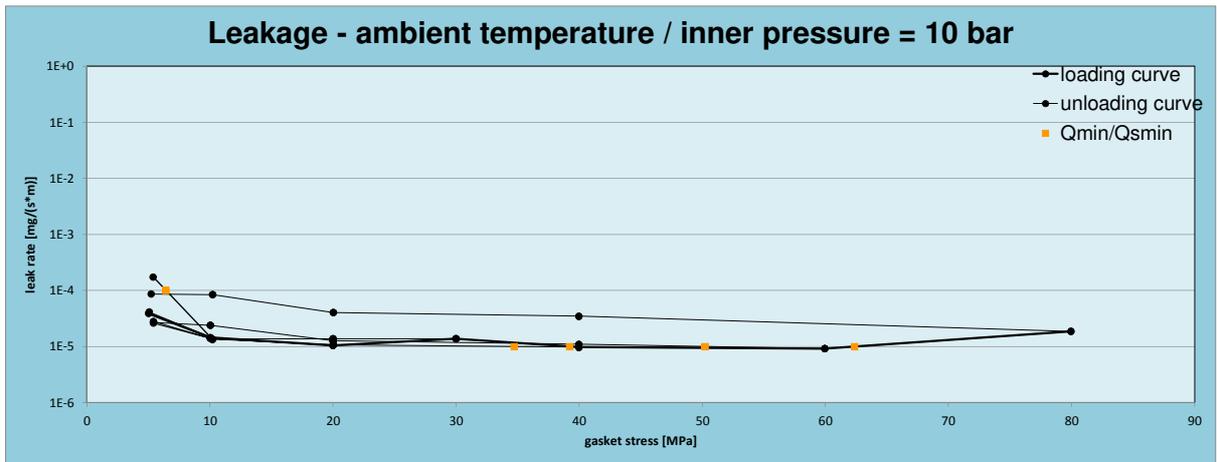

L [mg/(s*m)]	Q _{min/L} [MPa]	Minimum stress to seal Q _{min/L} (at assembly), Q _{Smin/L} (after off-loading) for p = 25 bar									
		Q _{Smin/L} [MPa]									
		Q _A = 20 MPa	Q _A = 30 MPa	Q _A = 40 MPa	Q _A = 60 MPa	Q _A = 80 MPa					
10 ⁻⁰	5	5	5	5	5	5					
10 ⁻¹	5	5	5	5	5	5					
10 ⁻²	5	5	5	5	5	5					
10 ⁻³	5	5	5	6	7	7					
10 ⁻⁴	5	5	9	9	10	14					
10 ⁻⁵	14	7									
10 ⁻⁶	20	18									
10 ⁻⁷											
10 ⁻⁸											

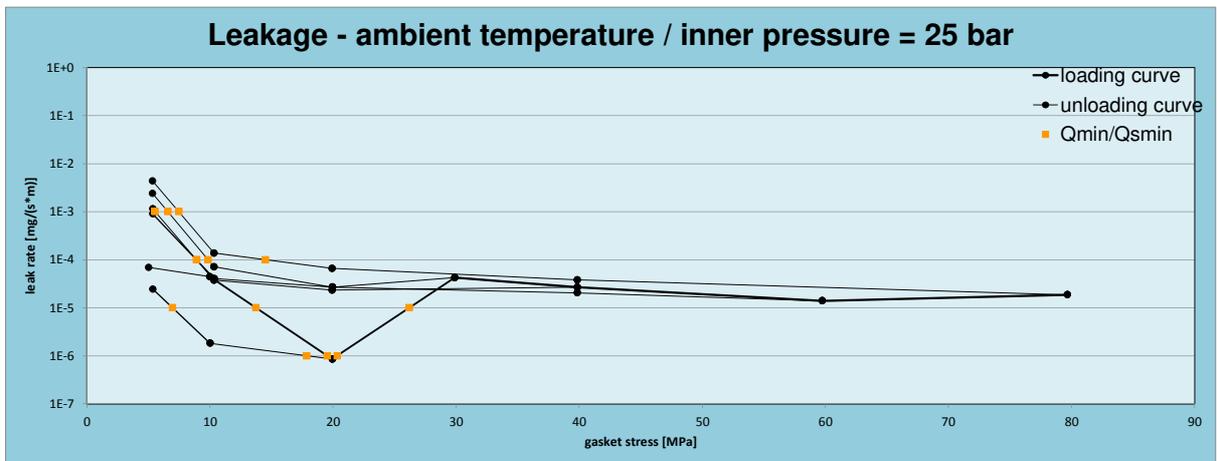

Company Address	IDT Industrie- und Dichtungstechnik GmbH Werk Kupferring, Gewerbering 6, 09456 Annaberg-Buchholz, Germany	According to DIN EN 13555 2014-07
Gasket Type	Elastik-Dichtung ED10 WS 7110/WS 7550	
Sealing element dimensions [mm]	49xs92x4.0	

L [mg/(s·m)]	Q _{min/L} [MPa]	Minimum stress to seal Q _{min/L} (at assembly), Q _{Smin/L} (after off-loading) for p = 40 bar							
		Q _{Smin/L} [MPa]							
		Q _A = 10 MPa	Q _A = 20 MPa	Q _A = 30 MPa	Q _A = 40 MPa	Q _A = 60 MPa	Q _A = 80 MPa		
10 ⁻⁰	5	5	5	5	5	5	5		
10 ⁻¹	5	5	5	5	5	5	5		
10 ⁻²	5	5	5	5	5	5	5		
10 ⁻³	6	6	8	12	12	13	12		
10 ⁻⁴	9	9	16	18	19	20	20		
10 ⁻⁵									
10 ⁻⁶									
10 ⁻⁷									
10 ⁻⁸									

